

Thermodynamic Constraints on the Magnetic Field Dependence of the Neutron Resonance in Cuprate Superconductors

Boldizsár Jankó

Materials Science Division, Argonne National Laboratory
9700 South Cass Avenue, Argonne, Illinois 60439, USA
(February 1, 2008)

In order to test the recently proposed connection between the neutron resonance and the specific heat anomaly in cuprates, the experimental specific heat data on $YBa_2Cu_3O_{6.93}$ and a theoretical estimate of the single particle fermionic contribution to the specific heat is used to provide an upper bound for the intensity of the neutron peak. The deduced peak intensity is similar in magnitude and temperature dependence to that observed in neutron scattering experiments, and it is constrained to decrease strongly under the influence of moderate magnetic fields oriented along the c -axis of the crystal. An explanation is proposed for the predicted suppression, based on the observation that the resonance intensity is very sensitive to superconducting phase correlations.

PACS numbers: 74.25.Bt, 74.25.Ha, 74.72.-h, 74.20.Mn

The resonance observed in inelastic neutron scattering remains one of the most heavily debated features of cuprate superconductivity. Its initial observation in $YBa_2Cu_3O_{6+x}$ [1] sparked numerous experimental [2] and theoretical [3–11] investigations. The detection of the resonance in $Bi_2Sr_2CaCu_2O_{8+\delta}$ [12], together with several recent studies suggesting a direct link between the resonance and salient features of other experiments [5, 13, 14], give further support to the suspicion, that the neutron resonance is a key phenomenon in high T_c superconductors.

Among the possible links, the one between the thermodynamic and magnetic anomalies deserves special attention. Taking a general argument by Scalapino and White [15] further, Demler and Zhang [16] pointed out that the emergence of the neutron resonance below the superconducting transition T_c results in a decrease in exchange energy that could account for the entire superconducting condensation energy. They proposed a simple relation between the resonance intensity $I_{\text{res}}(T)$ and the corresponding resonance contribution $C_{\text{res}}(T)$ to the specific heat:

$$C_{\text{res}}(T) = -\frac{J}{2\mu_B^2} \left(\frac{dI_{\text{res}}(T)}{dT} \right). \quad (1)$$

Here μ_B is the Bohr magneton and J is the nearest-neighbor spin-spin coupling. Dai and his collaborators [17] calculated $\partial T I_{\text{res}}(T)$ from neutron scattering data on $YBa_2Cu_3O_{6+x}$, used Eq.(1) to compute the specific heat anomaly corresponding to the neutron resonance, and compared the outcome to the data of Loram and his collaborators [18]. They concluded with the remarkable observation that the data are compatible with Eq.(1).

However, if Eq.(1) holds, then its inverse must also be valid.

$$I_{\text{res}}(T) = (2\mu_B^2/J) \int_T^{T_0} dt C_{\text{res}}(t), \quad (2)$$

where T_0 is an upper cutoff temperature, chosen to be larger than T^* , the resonance onset temperature. Thus, it should be possible to check the link between the thermodynamic and magnetic measurements by starting from the specific heat

measurements instead. After only a qualitative examination of typical specific heat data $C_{\text{el}}(T)$ (see, for example inset of Fig. 1) one concludes that performing such a task is not possible without an adequate account of the fermionic contribution to the specific heat. In fact, the specific heat jump in conventional superconductors is *entirely* due to the onset of a finite gap in the quasiparticle spectrum [19].

More important is the observation that if C_{res} is defined adequately, the inverted relation Eq.(2) allows one to impose a severe constraint on $I_{\text{res}}(T)$. It is known for some time, that the specific heat anomaly is removed [20–24] by a magnetic field of several Tesla oriented along the c -axis of the cuprate crystal. This means that Eq. (2), used with thermodynamic data taken in magnetic field, predicts large field induced effects on the resonance intensity. This is a new property of the neutron resonance, that has not been observed yet. The aim of this paper is therefore to point out that (a) an *upper bound* can be given for $C_{\text{res}}(T)$ in $YBa_2Cu_3O_{6.93}$, which in turn yields a reasonable account of $I_{\text{res}}(T)$, (b) the magnetic field sensitivity of $C_{\text{res}}(T)$ *constrains* $I_{\text{res}}(T)$ to be strongly field dependent, and (c) an intimate connection exists between the presence of a sharp resonance and superconducting long range order. This last observation leads to a natural explanation of the predicted field-induced suppression in resonance intensity.

The procedure for obtaining an upper bound for $C_{\text{res}}(T)$ is based on the observation that one can give a lower bound for the specific heat contribution $C_f(T)$ of single particle fermionic excitations. The fermionic specific heat contribution can be calculated from $\Omega_f(T, V)$, corresponding to the fermionic part of thermodynamic potential [25]

$$\Omega_f(T, V) = -\frac{1}{\beta} \text{Tr} \sum_{\mathbf{k}, \ell, \sigma} \left\{ \ln[(G_{\mathbf{k}, \ell})^{-1}] - \Sigma_{\mathbf{k}, \ell} G_{\mathbf{k}, \ell} \right\}, \quad (3)$$

where the single particle fermion propagator has the Nambu form $G_{\mathbf{k}, \ell} = (i\zeta_\ell - \epsilon_{\mathbf{k}}\tau_3 - \Delta_{\mathbf{k}}\tau_1)^{-1}$, corresponding to the Bardeen-Cooper-Schrieffer (BCS) self energy $\Sigma_{\mathbf{k}, \ell} = \Delta_{\mathbf{k}}\tau_1$; τ_i are Pauli matrices, $\zeta_\ell = (2\ell + 1)\pi k_B T$, and $\Delta_{\mathbf{k}}(T)$ is the superconducting gap. After performing the trace over the Pauli matrices, and the Matsubara sum, one obtains

$$\Omega_f(T, V) = \sum_{\mathbf{k}, \sigma} \left\{ \frac{2}{\beta} \ln[1 - f_{\mathbf{k}}] - E_{\mathbf{k}} + \frac{\Delta_{\mathbf{k}}^2}{2E_{\mathbf{k}}} (1 - 2f_{\mathbf{k}}) \right\}, \quad (4)$$

where $f_{\mathbf{k}} = [1 + \exp(\beta E_{\mathbf{k}})]^{-1}$ is the Fermi function. This is, not surprisingly, the usual form of the BCS thermodynamic potential [19], since in a conventional superconductors the elementary excitation are fermionic in nature.

The same statement does not necessarily hold for the cuprate superconductors. It was argued [16] that the specific heat jump in the cuprates is in large part due to the appearance of new bosonic degrees of freedom below T_c . The degradation [18] of the specific heat jump into an anomalous cusp in the underdoped regime adds further support to the possibility that jump is caused by the presence of bosonic excitation in the superconducting state. The expression in Eq. (4) will be used to separate from C_{el} the part that could, in principle, be due to bosonic excitations. This will be done by subtracting from C_{el} the fermionic contribution, computed from Eq. (4) and the thermodynamic relation $C_f(T) = -T\partial^2\Omega_f(T, V)/(\partial T)^2$. There is no information available on the temperature dependence of $\Delta_{\mathbf{k}}(T)$ in $YBa_2Cu_3O_{6+x}$. Under these circumstances it is more useful to provide a controlled lower bound for the fermionic specific heat. This is possible to achieve by taking the low temperature gap value $\Delta \simeq 25$ meV from tunneling measurements [26], and calculating $C_f(T)$ under the assumption that Δ is *constant at all temperatures*. In this way one obtains a lower bound for the fermionic specific heat contribution, as compared to the case when $\Delta(T)$ is decreasing with increasing temperature. Clearly the constant gap model systematically *underestimates* $C_f(T)$ in a system such as $YBa_2Cu_3O_{6.93}$, where $\Delta(T)$ is known to close near T_c . In the underdoped $YBa_2Cu_3O_{6+x}$ samples, due to the onset of the pseudogap, the constant gap model becomes an even better approximation [27]. Unfortunately, no tunneling data is available yet for such crystals.

Within the constant gap model Eq. (4) gives the following result for the fermionic specific heat

$$C_f(T) = \frac{k_B}{2} \sum_{\mathbf{k}} \text{sech}^3\left(\frac{\beta E_{\mathbf{k}}}{2}\right) \left[(\beta \epsilon_{\mathbf{k}})^2 \cosh\left(\frac{\beta E_{\mathbf{k}}}{2}\right) + (\beta^3 \Delta_{\mathbf{k}}^2 E_{\mathbf{k}}) \sinh\left(\frac{\beta E_{\mathbf{k}}}{2}\right) \right] \quad (5)$$

The anomalous part, $C_{res}(T)$, will be defined as the difference in the measured [18] electronic specific heat $C_{el}(T)$ and the fermionic contribution

$$C_{res}(T) \simeq C_{el}(T) - C_f(T). \quad (6)$$

The specific heat data of Loram *et al.* for $YBa_2Cu_3O_{6.93}$, displayed in the inset of Fig.1, together with Eqs. (2),(5)-(6), can now be used to compute the temperature dependence of the neutron resonance, as predicted by the thermodynamic data. At low temperatures this procedure gives

$I_{res}(0) \sim 0.01 \mu_B^2 \text{f.u.}^{-1}$, to be compared to the corresponding experimental value of $0.06 \pm 0.04 \mu_B^2 \text{f.u.}^{-1}$, where f.u. stands for formula unit.

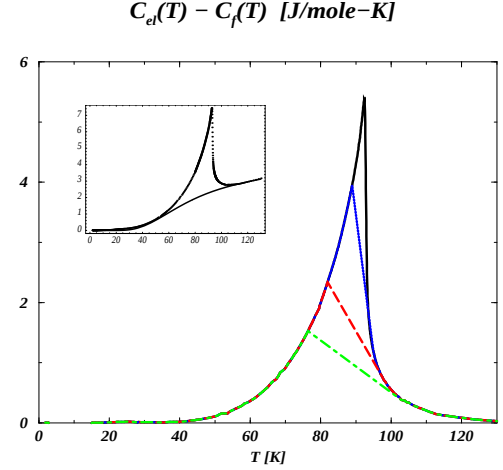


FIG. 1. **Inset:** The measured specific heat $C_{el}(T)$ (dots), and the lower bound for the fermionic contribution $C_f(T)$ (solid line), obtained by numerical evaluation of Eq.(5), using an s-wave gap $\Delta = 25$ meV at all temperatures. The normal state density of states was fitted to reproduce the normal state data near T_0 . **Main figure:** The anomalous part, obtained by subtracting the calculated lower bound, $C_f(T)$, from the experimental data, $C_{el}(T)$. The effect of the magnetic field along the c -axis of the crystal is simulated by using the results of Ref. [21]. The peak of the anomaly is gradually shifted to lower temperatures and reduced: 100% and 93 K (zero field, solid curve), to 71% and 89 K ($B = 1$ T, dotted curve), 45% and 81 K ($B = 3$ T, dashed curve), and finally 30% and 75 K ($B = 6$ T, dash-dotted curve)

While the deduced intensity is still the same order of magnitude as the experimental value of Ref. [17], the agreement is less striking. On the other hand, the fact that the resonance intensity required by the thermodynamic changes is smaller than that observed in neutron scattering supports the possibility that the source of superconducting condensation energy is in fact the gain in exchange energy, as suggested by Demler and Zhang [16]. The deduced $I_{res}(T)$ is somewhat affected by ambiguities in choosing T_0 , by experimental errors in the tunneling gap Δ , and in the specific heat data itself, introduced by the necessary phonon subtraction. The normalized zero field intensity is shown as the solid curve in Fig. 2, together with the experimental data from Ref. [17]. The agreement is satisfactory except near the transition temperature $T_c \sim 92.5$ K, where the intensity is overestimated. This can be considered an indirect signature of temperature dependence of the superconducting gap.

As pointed out by several groups [20–22], the specific heat anomaly near T_c is removed in $YBa_2Cu_3O_{6.93}$ by a magnetic field $B \sim 10$ T along the c axis, while $C_{el}(T)$ away from T_c is unaffected. This is highly unusual, since the applied magnetic field is only a small fraction of the upper critical field $B_{c2} \sim 100$ T. Similar effects have been recently documented

in other cuprate materials as well [23,24]. The recent work of Junod and coworkers [24] presents an especially detailed account of the field dependence of the specific heat anomaly. They contrast the behavior seen in the cuprates with that in a low T_c superconductor (Nb-Zr alloy), where the anomaly is pushed to lower temperatures, but never removed. Indeed, the behavior seen in cuprates seems to go beyond the conventional framework, according to which as long as T_c is finite, the specific heat jump is also finite [28].

The most detailed set of data for the field dependence of the anomaly in $YBa_2Cu_3O_{6.93}$ was presented in Ref. [21]. In these measurements, however, the phonon background was not subtracted, as in the data Loram *et al.* used above. In order to avoid subtraction problems, the finite field specific heat jumps were obtained by imposing on Loram and coworkers' zero field data [18] the suppression in the height and the shift towards lower temperatures of the specific heat maximum observed by Junod's group [21]. The result is shown in the main part of Fig. 1.

When field-suppressed specific heat anomalies are used in Eq.(2), the resulting temperature dependence of the deduced resonance intensity deviates from what was measured in zero field, as shown in Fig. 2. In fact, these results show that $I_{\text{res}}(B, T)$ should be depleted at low temperatures beyond the present experimental error when $B > 6 T$ (see figure). Bourges *et al.* [29] measured the neutron resonance in magnetic field and found $I_{\text{res}}(T \sim 6 \text{ K})$ to be *insensitive* to fields of order $B \sim 12 T$ oriented along the *ab* plane of the sample. Their result does not invalidate the claim of Dai *et al.*, since in that geometry the specific heat anomaly is only moderately depleted, and not removed by the field [21]. However, the measurement of $I_{\text{res}}(B, T)$ with **B** along the c-axis seems to be a crucial experiment for not only establishing the validity of Eqs.(1) and (2), but also to gain important insight into the nature of the neutron resonance itself.

The strong magnetic field dependence of the resonance predicted by the above procedure raises immediately a key question: What is the main mechanism responsible for inducing such a large change in the neutron intensity? In the remainder of this paper I will argue that there is an intimate connection between the resonance and correlations in the phase of the superconducting order parameter. This connection, besides offering a natural explanation for the field sensitivity of the resonance, also seems to have direct relevance to some puzzles in the zero field properties of the resonance, like the existence of the resonance in bilayer materials only [2], and the presence of a broad precursor resonance in the pseudogap state [17].

There are three important clues to consider. First, irrespective of doping, a sharp resonance is observed only below T_c , after off diagonal long range order is established. Second, the magnetic field required to affect the resonance is predicted by the above analysis to be much smaller than B_{c2} . Scanning tunneling spectra [30] show that such fields do not broaden out the superconducting singularities significantly. Finally, a c-axis field strongly affects the specific heat jump and the resonance, but only mild changes are observed if the field is

along the *ab*-plane [21], consistent with the results of Bourges *et al.* [29]. The strong dependence on the field direction suggests that Zeeman splitting is irrelevant and that the resonance is not affected by shielding currents along the c-axis itself, when the field is parallel to the CuO_2 planes. On the contrary, the resonance is affected considerably by the presence of *in-plane* shielding currents circulating around the cores of Abrikosov vortices, when the field is parallel to the c-axis. As discussed in more detail below, this translates to the statement that in-plane long range coherence as well as short range c-axis coherence (intra-bilayer) does matter for the resonance, whereas long range c-axis phase coherence does not.

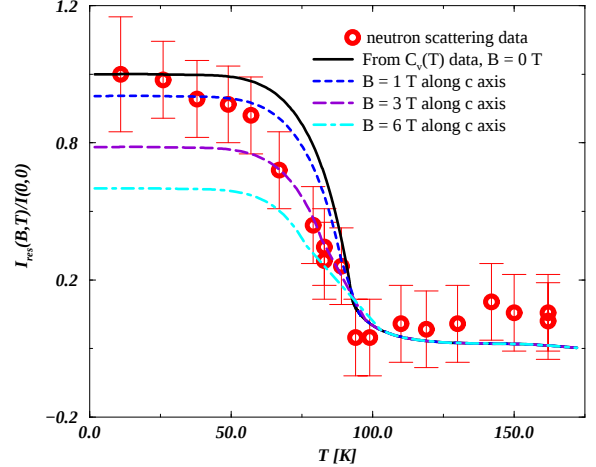


FIG. 2. The neutron resonance intensity for the optimally doped compound $YBa_2Cu_3O_{6.93}$: Dots are the zero field results of Ref. [17]; lines were derived from specific heat data of Refs. [18,21] as explained in the text. All the curves were normalized with the zero field, low temperature value of the deduced intensity, $0.01\mu_B^2 \text{ f.u.}^{-1}$.

In order to make these observations more transparent, it is instructive to examine the bare spin susceptibility, where the phase dependence is indicated explicitly [31]

$$\chi^0(\mathbf{Q}, i\Omega_n) = \chi_{GG}^0(\mathbf{Q}, i\Omega_n) + \frac{1}{\beta} \sum_{\mathbf{p}, m} \chi_{FF}^0(\mathbf{Q} - \mathbf{p}, i\Omega_n - i\omega_m) \Lambda(\mathbf{p}, i\omega_m). \quad (7)$$

Here $\chi_{GG}^0(\mathbf{Q}, i\Omega_n)$ and $\chi_{FF}^0(\mathbf{Q}, i\Omega_n)$ are the normal and superconducting contributions to the bare susceptibility, $\chi_{FF}^0(\mathbf{q}, \omega_n) = \frac{1}{\beta} \sum_{\mathbf{k}, \ell} F_{\mathbf{k}+\mathbf{q}}(\zeta_\ell + \omega_n) F_{\mathbf{k}}(\zeta_\ell)$, and $\Omega_m = 2m\pi k_B T$. A similar expression holds for $\chi_{GG}^0(\mathbf{Q}, i\Omega_n)$, but with the Gor'kov propagators replaced by the diagonal part of the superconducting Green's function. The function $\Lambda(\mathbf{p}, i\omega_m)$ is the Fourier and Matsubara transform of the charge displacement correlation function [32], $\Lambda(\mathbf{r} - \mathbf{r}', \tau - \tau') = \langle T_\tau [e^{i\phi(\mathbf{r}, \tau)} e^{-i\phi(\mathbf{r}', \tau')}] \rangle$, and $\phi(\mathbf{r}, \tau)$ is the phase of the superconducting order parameter at position $\mathbf{r}$ and imaginary time τ .

Equation (7) can provide new insights even for the zero field case. In the absence of phase fluctuations, corresponding to

the BCS mean field level, $\Lambda(\mathbf{q}, i\omega_m) = \beta\delta(\mathbf{q})\delta_{m,0}$, and one obtains the standard result used as a starting point in essentially all theoretical descriptions of the resonance [3–11]. In zero external field the phase fluctuations are uniform in space and Gaussian around the mean phase ϕ_0 , and consequently the correlator $\Lambda(\mathbf{p}, \omega)$ is still dominated by its low frequency, long wavelength value $\Lambda(0, 0) = \exp[-\langle\delta\phi^2\rangle]$. Thus, phase fluctuations reduce the contribution of the anomalous susceptibility χ_{FF}^0 , and consequently the resonance intensity [3–11], since neither the bare, nor the RPA-dressed χ_{GG} can account on its own for the resonance. In single layer materials, due to the weak interplane coupling and strong two dimensionality, quantum phase fluctuations can be quite large, and consequently Λ very small. In contrast to single layer materials, the strong Josephson coupling between bilayers can stabilize the superconducting state with a rigid phase. This could be the main reason why the neutron resonance has only been observed in bilayer materials, and not in single layer materials, such as $La_{2-x}Sr_xCuO_4$ [2]. The broad maximum observed [17] in the *pseudogap regime* of underdoped $YBa_2Cu_3O_{6+x}$ could be the precursor of the resonance below T_c , provided that strong pairing fluctuations are present in this regime [33].

In the Abrikosov vortex phase induced by a field along the c-axis, the weight of $\Lambda(\mathbf{p}, \omega)$ is no longer concentrated at long wave lengths and low frequencies. As shown by Glazman and Koshelev [34], the vortex lattice destroys the off-diagonal long range order in the planes at finite T , while long range order along the field direction is broken only at elevated temperatures. For the in plane correlations, they find $\lim_{r \rightarrow \infty} \Lambda(r, z=0) = \lim_{r \rightarrow \infty} \exp[-r/\ell(B)] = 0$, where $\ell(B) \propto B^{-1/2}$ is the in-plane phase correlation length in magnetic field. Thus, the field will induce a momentum broadening $\delta\mathbf{p} \propto \sqrt{B}$ in the resonance, and a reduced intensity. In general, a form of $\Lambda(\mathbf{q}, \omega)$ that deviates from the singular mean field result, will upset the resonance condition satisfied by the zero field susceptibility for $Q = (\pi, \pi, \pi)$; $\omega = \omega_0$.

The arguments presented above are quite general and consequently have direct relevance not only to the magnetic field dependence of the neutron resonance, but also to the finite field behavior of optical conductivity, tunneling density of states, Raman scattering cross section, and other spectroscopic and thermodynamic properties of cuprate superconductors. A detailed study of all these effects is currently under way, and will be reported in a later publication.

I am grateful to Dr. John W. Loram for making his specific heat data available. I would also like to thank Prof. A. A. Abrikosov, Dr. Joel Mesot, and especially Dr. Michael R. Norman for numerous discussions, and to Dr. Philippe Bourges, Dr. Pengcheng Dai and Dr. Herbert A. Mook for correspondence. This research was supported in part by the NSF under awards DMR91-20000 (administrated through the Science and Technology Center for Superconductivity), and the U.S. DOE, BES, under Contract No. W-31-109-ENG-38.

- [1] J. Rossat-Mignod *et al.* Physica C, **185-189**, 86 (1991).
- [2] For a recent review, see T.E. Mason in *Handbook on the Physics and Chemistry of Rare Earths*, Edited by K.A. Gschneider Jr. *et al.* (cond-mat/9812287).
- [3] M. Lavagna and G. Stemmman, Phys. Rev. B **49**, 4235 (1994)
- [4] S. Quinlan and D.J. Scalapino, Phys. Rev. B **51**, 497 (1995); N. Bulut and D.J. Scalapino, Phys. Rev. B **51**, 5149 (1996)
- [5] E. Demler and S.-C. Zhang, Phys. Rev. Lett. **75**, 4126 (1995); Phys. Rev. B **58**, 5719 (1998).
- [6] D.Z. Liu, Y. Zha and K. Levin, Phys. Rev. Lett. **75**, 4130 (1995).
- [7] I.I. Mazin and V. Yakovenko, Phys. Rev. Lett. **75**, 4134 (1995).
- [8] L. Lin, S. Chakravarty, and P.W. Anderson, Phys. Rev. Lett. **78**, 3559 (1997).
- [9] A.A. Abrikosov, Phys. Rev. B **57**, 8656 (1998).
- [10] D.K. Morr and D. Pines, Phys. Rev. Lett. **81**, 1086 (1998).
- [11] J. Brinckmann and P.A. Lee, Phys. Rev. Lett. **82**, 2915 (1999).
- [12] H. Fong *et al.*, Nature **398**, 588 (1999).
- [13] J.C. Campuzano *et al.*, Phys. Rev. Lett. **83**, 3709 (1999); Ar. Abanov and A.V. Chubukov, Phys. Rev. Lett. **83**, 1652 (1999).
- [14] D. Munzar, C. Bernhard, and M. Cardona, Physica C **318**, 547 (1999). J.P. Carbotte, E. Schachinger and D.N. Basov, Nature **401**, 354 (1999).
- [15] D.J. Scalapino and S.R. White, Phys. Rev. B **58**, 1347 (1998).
- [16] E. Demler and S.-C. Zhang, Nature **396**, 733 (1999).
- [17] P. Dai *et al.*, Science **284**, 1344 (1999).
- [18] J.W. Loram *et al.*, J. Supercond. **7**, 243 (1994).
- [19] G. Rickayzen, *Theory of Superconductivity*, John Wiley & Sons, NY, 1964.
- [20] S.E. Inderhees *et al.*, Phys. Rev. Lett. **66**, 232 (1991).
- [21] E. Janod *et al.*, Physica C, **234**, 269 (1994). M. Roulin, A. Junod, and E. Walker, Physica C **260**, 257 (1996).
- [22] N. Overend, M.A. Howson, I.D. Lawrie, Phys. Rev. Lett. **72**, 3238 (1994).
- [23] A. Carrington *et al.*, Phys. Rev. B **55**, R8674 (1997).
- [24] A. Junod, A. Erb and Ch. Renner, Physica C **318** 333 (1999).
- [25] A.A. Abrikosov, L.P. Gor'kov and I.E. Dzyaloshinski, *Methods of Quantum Field Theory in Statistical Physics*, Prentice Hall, Englewood Cliffs, N.J. 1963.
- [26] J.M. Valles *et al.*, Phys. Rev. B **44**, 11986 (1994); J. Y. T. Wei, *et al.*, Phys. Rev. Lett. **81**, 2542 (1998).
- [27] H. Ding *et al.*, Nature **382**, 51 (1996).
- [28] A. L. Fetter and P.C. Hohenberg, *Theory of Type II superconductors*, Vol. II, Chapter 14 of *Superconductivity* Edited by R.D. Parks (Dekker, NY 1969).
- [29] P. Bourges *et al.*, Physica B, **234-236**, 830 (1997).
- [30] Ch. Renner *et al.*, Phys. Rev. Lett. **80**, 149 (1998); E. D. Hudson *et al.*, Science **285**, 88 (1999); A. Yazdani *et al.*, Phys. Rev. Lett. **83**, 176 (1999).
- [31] The corresponding expression for the c-axis conductivity has recently been suggested by L.B. Ioffe and A.J. Millis, Science **285**, 1241 (1999).
- [32] See, for example B. Jankó and V. Ambegaokar, Phys. Rev. Lett. **75**, 1154 (1995) and references therein.
- [33] See J. Maly, B. Jankó and K. Levin, Physica C **321**, 113 (1999), and references therein.
- [34] L.I. Glazman, and A.E. Koshelev, Phys. Rev. B **43**, 2835 (1991).